

CONSTRUCTION INDUSTRY COUNCIL

CIC GREEN PRODUCT CERTIFICATION

Assessment Standard

Technical Requirements

Cement



CIC GREEN
PRODUCT CERTIFICATION

(Version 2)

Copyright © 2026 Construction Industry Council

All rights reserved. No part of this document may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, whether electronic or mechanical, including photocopying and recording, without the written permission of the Construction Industry Council. If there is any inconsistency or ambiguity between the English version and the Chinese version, the English version shall prevail.

Cement

Summary of Assessment Criteria

CORE CRITERIA

Criteria	Requirements	Verification	Point		Index	
			Basic	+Bonus		
CARBON						
CFP Quantification	Provide a life cycle assessment report with the carbon footprint of products (CFP) in tCO ₂ e/t of product, covering at least A1 to A3 and meet the requirement below.	CFP quantification report OR Environmental Product Declaration (EPD)	50	+10/+20 +30/+40	4.1.1	
	Points					CFP (tCO ₂ e / t of product)
	50 Basic + 40 Bonus					≤0.658
	50 Basic + 30 Bonus					0.659-0.790
	50 Basic + 20 Bonus					0.791-0.966
	50 Basic + 10 Bonus					0.967-1.097
50 Basic	≥1.098					
		Subtotal:	50	+40		

NON-CORE CRITERIA

Criteria	Requirements	Verification	Points	Index
			+Bonus	
RESOURCE				
Waste Management	The manufacturer implements a waste management system aimed at minimizing waste generation and promoting the recycling of materials produced during the manufacturing process.	Waste Management Report	+5	4.2.1
ENVIRONMENT				
Regional Materials	Meet 95% localisation degree of raw materials.	Self-prepared calculation report with relevant supporting e.g. Purchase order, delivery note	+5	4.3.1
PERFORMANCE				
Advancement	Products that achieve a valid “Product Conformity Certification Scheme for Cement Products” certificate	Valid certificate of Product Conformity Certification Scheme	+5	4.4.1
INNOSMART				
Innovations & Additions	Adopt new practice, technology and strategy; <i>OR</i> Achieve exemplary performance	Narrative with supporting documents	+5	4.5.1
		Subtotal:	+10 (Maximum)	

TABLE OF CONTENTS

1. INTRODUCTION.....	1
1.1 PURPOSE.....	1
1.2 BACKGROUND AND SCOPE	2
2. DEFINITIONS & ACRONYMS	2
2.1 TERMS RELATING TO CEMENT PRODUCTION.....	2
2.2 TERMS RELATING TO LIFE CYCLE ASSESSMENT (LCA).....	3
3. CFP STUDY – PRODUCT CATEGORY RULE (PCR)	3
3.1 GOAL.....	3
3.2 PRODUCT DESCRIPTION AND DECLARED UNIT	3
3.3 SYSTEM BOUNDARY	4
3.3.1 Overview of Process Map of Cement Manufacturing	4
3.3.2 Sources of GHG Emissions	5
3.3.3 Guidelines for Inclusion of Similar Products	13
4. REQUIREMENTS.....	14
4.1 CARBON	14
4.1.1 CFP Quantification - Core Criteria.....	14
4.2 RESOURCE	15
4.2.1 Waste Management – Non-core Criteria	15
4.3 ENVIRONMENT.....	16
4.3.1 Regional Materials – Non-core Criteria	16
4.4 PERFORMANCE	16
4.4.1 Advancement – Non-core Criteria	16
4.5 INNOSMART	17
4.5.1 Innovations & Additions – Non-core Criteria	17
5. SCORING.....	19
6. REFERENCES.....	20

1. INTRODUCTION

1.1 PURPOSE

The CIC Green Product Certification (the “Scheme”) is a green product labelling scheme, owned by the Construction Industry Council (CIC) and implemented by the Hong Kong Green Building Council (HKGBC). The primary goal of the scheme is to support Hong Kong’s transition to a low-carbon economy by encouraging the adoption of environmentally friendly construction practices.

With the Green Product Certification, various stakeholders, including consumers, building professionals, construction practitioners, and policymakers, can easily and unequivocally identify environmentally preferable construction materials and building products. This certification serves as a reliable indicator of a product’s sustainability, helping to drive market demand for greener options.

To ensure the credibility and effectiveness of the certification, the CIC and the HKGBC have jointly developed this Technical Assessment Standards (the “Standard”), which sets out the assessment criteria and their benchmarks to govern the application and award of a grade under the Scheme. The comprehensive assessment evaluates the overall sustainability of construction materials and building products across multiple dimensions. These dimensions include environmental impact, resource efficiency, technical performance, and the use of smart manufacturing technologies.

The Standard is divided into two main parts:

- General Requirements (Refer to General Requirements provided in separate document). This part introduces Scheme's framework, outlines the application procedure, and details the grades.
- Technical Requirements (This document refers). This part defines the principles, requirements, and guides for quantifying and reporting the products’ carbon footprint (CFP), along with other sustainability assessment criteria and scoring standards.

This Standard neither modifies nor supersedes laws and regulations. Compliance with this Standard is not a substitute for, and does not assure, compliance with any applicable laws or regulations. Compliance with all applicable laws and regulations is a prerequisite for the manufacturing and marketing of the product.

The Scheme is owned by the Construction Industry Council (CIC), 38/F, COS Centre, 56 Tsun Yip Street, Kwun Tong, Kowloon, Hong Kong; and operated by Hong Kong Green Building Council (HKGBC), 1/F, Jockey Club Environmental Building, 77 Tat Chee Avenue, Kowloon Tong, Hong Kong, Phone: +852 3994 8888, Email: cicgpc@hkgbc.org.hk

1.2 BACKGROUND AND SCOPE

Cement is extensively used in the construction industry as an essential ingredient in producing ready-mixed concrete. As cement production is energy-intensive, consuming large quantities of fuel during manufacturing, especially the kilning process, the cement industry alone generated approximately 7% of the global anthropogenic carbon dioxide (CO₂) emissions and is the third-largest industrial energy consumer. (IEA, 2018).

This Standard applies to cement and inter-ground or blended mixtures of cement with other materials, which may include gypsum, limestone, fly ash, blast furnace slag, or naturally occurring pozzolanic materials, e.g. CEM I, CEM II, CEM III.

- CEM I: Portland cement consists of 95% to 100% clinker with a maximum of 5% minor additional constituents (such as limestone).
- CEM II: A composite cement containing clinker, and up to 35% of another single constituent such as fly ash, slag, or limestone.
- CEM III: A composite cement consisting of clinker, and a higher percentage of blast furnace slag ranging from 36%-95%.

2. DEFINITIONS & ACRONYMS

2.1 TERMS RELATING TO CEMENT PRODUCTION

Bypass dust: The discarded dust from the bypass system de-dusting unit of suspension pre-heater, pre-calciner, and grate pre-heater kilns, consisting of fully calcined kiln feed material.

CaO: Calcium Oxide.

Cement: A hydraulic binder, i.e. a finely ground inorganic material which, when mixed with water, forms a paste which sets and hardens by means of hydration reactions and which, after hardening, retains its strength and stability even under water.

Cement kiln dust (CKD): The discarded dust from the long dry and wet kiln system de-dusting units, consisting of partly calcined kiln feed material. Extraction and discarding of the bypass dust and CKD serve to control excessive circulating elements input (alkali, sulphur, chlorine), particularly in the case of low alkaline clinker production. The term “CKD” is sometimes used to denote all dust from the cement kilns, i.e. also from the bypass systems.

Clinker: A semi-finished product of kiln which is ground to make cement; and it is obtained by grinding and burning a mixture of mainly calcareous and argillaceous materials in the kiln.

CSI: Cement Sustainability Initiative.

<i>Mineral components (MICs):</i>	Natural or artificial mineral materials with hydraulic properties, used as clinker or cement substitutes (e.g. blast furnace slag, fly ash, pozzolana, etc.).
<i>MgO:</i>	Magnesium Oxide.
<i>Raw Meal:</i>	The mixture of raw materials in the required chemical composition for the production of cement clinker.
<i>TOC:</i>	Total organic carbon.
<i>WBCSD:</i>	World Business Council for Sustainable Development.
<i>WRI:</i>	World Resources Institute.

2.2 TERMS RELATING TO LIFE CYCLE ASSESSMENT (LCA)

For terms related to LCA, please refer to General Requirements.

3. CFP STUDY – PRODUCT CATEGORY RULE (PCR)

3.1 GOAL

The goal of carrying out a CFP study is to calculate the potential contribution of a specific cement product to climate change expressed as CO_{2e} by quantifying all significant GHG emissions and removals over the cement product's life cycle.

The CFP study reports submitted by Applicants will be evaluated by Validation and Verification Body. This is facilitated by identical CFP quantification and communication requirements under the same product category as stipulated in Annex C of ISO 14067:2018.

This section sets the PCR of cement products for CFP quantification and reporting under the Scheme following the four phases of life cycle assessment (LCA), i.e. goal and scope, LCI, LCIA, and life cycle interpretation. Applicants should refer to the principles and methodology detailed in ISO 14067:2018 and WBCSD (2011) for CFP quantification and reporting.

3.2 PRODUCT DESCRIPTION AND DECLARED UNIT

The CFP study should be conducted on a per-product basis. Refer to Section 1.2 for the description of the Cement product covered under this PCR.

The declaration unit is defined as 1 tonne of cement product. The CFP shall be reported in tCO_{2e}.

The CFP Study shall include at least the following description of the product:

- Mix composition
- Specified compressive strength

3.3 SYSTEM BOUNDARY

The PCR is developed to capture the product stage A1-A3 (Cradle-to-gate) as defined in ISO 14025:2006, ISO 14067:2018, BS EN 15804:2012, ISO 21930:2017 or GB/T 24067-2024.

3.3.1 Overview of Process Map of Cement Manufacturing

The key unit processes of cement manufacturing within the stipulated system boundary are presented in Figure 1 for CFP quantification. The raw materials of cement (i.e. calcium silicate minerals) are first quarried or mined and transferred to the manufacturing facility to be crushed into fine powder, blended and milled before entering into a pre-heater and eventually a large rotary kiln where materials reach a temperature of 1,450°C. The most carbon-intensive stage of the process is pre-calcining; the chemical reactions in the calcination process typically emit 60-70% of direct CO₂ emissions. Fuel combustion generates the rest 30-40% of direct CO₂ emissions (IEA, 2018). The clinker or kiln product is cooled to ensure the maximum yield for the compound that contributes to the hardening properties of cement, and the excess heat is typically routed back to the preheater units. Supplementary cementitious materials such as slag, fly ash, fine limestone, pozzolana or other materials can be interground or blended to replace part of the clinker. Prior to packaging, gypsum is added to the clinker to control the setting time. The end product is a very fine-grained blended cement (≈ 10 micron).

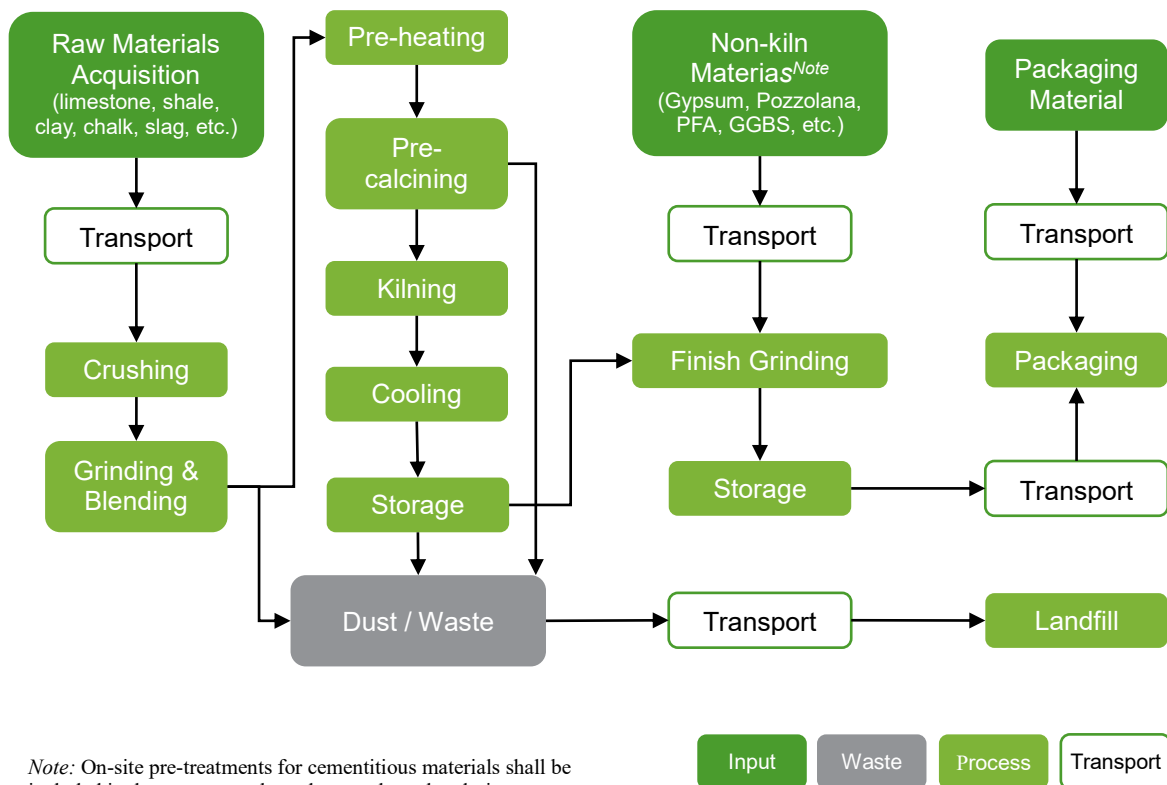


Figure 1 Process Map of Cement Manufacturing¹

3.3.2 Sources of GHG Emissions

The qualitative and quantitative data for inclusion in the life cycle inventory shall be collected for all unit processes that are included in the predefined system boundary and process map. The assessment and reporting of GHG emissions and removals of cement are divided into direct emissions and indirect emissions.

Direct vs. Indirect Emissions

The direct emissions stem from sources that are owned or controlled by the material supplier. The indirect emissions originate from sources that are controlled by third parties, but they are nonetheless related to the activities of the material supplier.

WBCSD (2013b)

The GHG assessment framework is developed based on the ISO 14067:2018 “Greenhouse gases — Carbon footprint of products — Requirements and guidelines for quantification” and the “CO₂ and Energy Accounting and Reporting Standard for the Cement Industry” issued by WBCSD (2011). The Applicant is required to quantify and report the carbon footprint of a specific cement product using the CFP quantification tool (in Excel format) provided under the Scheme, or providing an EPD report compliance with applicable standards, including ISO 14025:2006, ISO 14067:2018, ISO 21930:2017, GB/T 24067-2024, GB/T 24025-2009 or BS EN 15804:2012.

The assessment of the GHG emissions generated and removed throughout the cement product processes shall be made based on an attributional approach, i.e. by assessing the carbon contents associated with inputs and outputs of a specific process. For instance, the GHG emissions of by-product gases, either for internal or external use, should first be subtracted within the process boundary. Subsequently, the GHG emitted from the fuel combustion and chemical reduction owing to the use of the by-product gas associated with the assessed product should be assessed and reported in the subsequent processes.

3.3.2.1 Direct Emissions

The sources of direct GHG emissions include i) raw material calcinations and combustion; ii) combustion of kiln fuels; and iii) combustion of non-kiln fuels.

i) Raw Materials Calcination and Combustion

CO₂ will be released from the following three sources related to raw materials:

- Calcination of carbonates during the pyro processing of raw meal for clinker production²; and

¹ The figure shows a typical cement production process. There are older, much less efficient technologies, for example the wet kiln into which the raw material is fed as slurry and not as a powder (dry kiln).

² Calcination CO₂ can be calculated in two ways: based on the volume and carbonate content of the raw meal consumed (input method) or based on the volume and composition of clinker produced (output method) plus dust leaving the system. Output method is adopted in this Guide and the CFP assessment tool. However, Applicants may choose to apply the raw meal-based input method of the clinker-based output method based on data availability.

- Calcination of cement kiln dust (CKD) and bypass dust leaving the kiln system; and
- Combustion of total organic carbon (TOC) contained in raw materials.

Emissions of methane (CH₄) and nitrous oxide (N₂O) from cement kilns are insignificant due to the high combustion temperatures in the kilns. The other GHGs covered by the Kyoto Protocol (PFC, HFC, SF₆, NF₃) are irrelevant in the cement context and can therefore be ignored.

Calcination of Raw Materials for Clinker Production³

CO₂ from the calcination of carbonates in the raw meal shall be calculated based on the volume of clinker produced and an emission factor per tonne of clinker. The emission factor shall be determined based on the measured CaO and MgO contents of the clinker and corrected if relevant quantities of CaO and MgO in the clinker stem from non-carbonate sources. This could be the case when, for example, calcium silicate or fly ash being used as a raw material has entered the kiln. The determination of the emission factor for clinker shall be clearly documented. In the absence of any explicit data, a default of 535 kg CO₂/t⁴ clinker shall be used.

Calcination of Dust

CO₂ from bypass dust or CKD leaving the kiln system shall be calculated based on the complete volumes of dust leaving the kiln system and an emission factor. Bypass dust is usually fully calcined. Therefore, the emissions related to the bypass dust shall be calculated using the emission factor for clinker. CKD, as opposed to the bypass dust, is usually not fully calcined. The emission factor for CKD shall be determined based on the emission factor for clinker and the calcination rate of CKD, in accordance with Equation 1.

$$EF_{CKD} = \frac{\frac{EF_{cli}}{1 + EF_{cli}} * d}{1 - \frac{EF_{cli}}{1 + EF_{cli}} * d} \quad \text{Equation (1)}$$

where:

EF_{CKD} = emission factor of partially calcined cement kiln dust (tCO₂/t CKD).

EF_{cli} = plant specific emission factor of clinker (tCO₂/t clinker).

d = CKD calcinations rate (released CO₂ expressed as a fraction of the total carbonated CO₂ in the raw meal).

The calcination rate d of CKD shall preferably be based on the plant-specific data. However, if such data does not exist, a default value of 0 shall be used for dry process kilns as CKD is usually not calcined in this process. A default value of 1

³ The CO₂ emissions from the calcination of relatively small amounts of carbonates in fuel ashes added to the kiln system shall be accounted by the reporting of fuel CO₂ emissions. This is assured by determining the CO₂ emission factors for fuels based on the total carbon content of the fuels, which includes both total organic carbon (TOC) and total inorganic carbon (TIC). Materials with high contents of both TOC and TIC (e.g. municipal sewage sludge) can be regarded as fuel and/or raw material. In any case, the complete CO₂ emissions resulting from their use shall be accounted.

⁴ Guidelines for Accounting and Reporting of Greenhouse Gas Emissions for Enterprises in the Cement Industry (CETS-AG-02.01-V01-2024)

shall be used for other processes (half dry, half wet or wet). Should there be no plant-specific data on the dust volume, the Intergovernmental Panel on Climate Change (IPCC) default for CO₂ from discarded dust (2% of clinker CO₂) shall be used. However, using plant or company-specific data is preferred.

Combustion of Total Organic Carbon (TOC)

In addition to the inorganic carbonates, the raw materials used for clinker production usually contain a small fraction of organic carbon, which is mainly converted to CO₂ during the pyro-processing of the raw meal. CO₂ emissions from organic carbon in raw materials shall be quantified and reported for the sake of completeness of the inventory. Since their contribution to the overall emissions is small, a simplified self-calculating mechanism has been implemented in the CFP quantification tool using the following default values:

- Default raw meal to clinker ratio: 1.55
- Default TOC content of raw meal: 2 kg/t raw meal (dry weight, corresponding to 0.2%)

The Applicant is not required to analyse these emissions any further unless there are indications that the organic carbon is more relevant in their context. Furthermore, any volumes of dust leaving the kiln system are not automatically reflected in this default calculation. To analyse the TOC-related emissions in greater detail, manufacturers producing substantial quantities of dust should enter their plant-specific raw meal to clinker ratios. The plant-specific raw meal to clinker ratios should exclude the ash content of the fuels used in order to avoid double counting.

ii) Combustion of Kiln Fuels

Kiln fuels include all conventional and alternative fuels fed to the kiln system plus fuels used for drying and processing the raw materials or other kiln fuels, irrespective of the potential use of waste heat for the production of electrical power.

Conventional Fuels

Conventional kiln fuels are fossil fuels, e.g. coal, petcoke, fuel oil and natural gas. The preferred approach is to calculate CO_{2e} from conventional kiln fuels (the same applies to alternative and non-kiln fuels) based on fuel consumption, lower heating values, and match CO_{2e} emission factors. Fuel consumption and lower heating values of fuels should be regularly measured at the plant level. It is important to note that the applied heating value always has to match the status of the fuel, especially with respect to the correct moisture content during its weighing (raw coal or dried coal).

Default emission factors per GJ lower heating value are extracted from IPCC (2006 and 2019) and listed in the CFP quantification tool. Manufacturers are encouraged to use the plant or country-specific emission factors if reliable data is available. The emission factor of fuels shall be based on the total carbon content. Direct calculation of emissions based on fuel consumption (in tonnes) and fuel carbon content (in percent) is acceptable on condition that the material variations in the composition of fuel, and especially its water content, are adequately accounted for. Generally, the IPCC recommends the accounting for incomplete combustion of fossil fuels. In cement kilns, however, this effect is negligible, due to the very high

combustion temperature and a long residence time in kilns along with a minimal residual carbon found in clinker. Consequently, carbon in all kiln fuels shall be treated as fully oxidised.

Alternative Fuels

The cement industry increasingly uses a variety of alternative fuels, which are typically derived from waste. Therefore, without this application, the waste would have to be disposed of in some other forms, usually by landfilling or incineration. Alternative fuels include fossil fuel-based fractions, such as waste oil and plastics, and biomass fractions, such as waste wood and sewage sludge. They serve as a substitute for conventional fossil fuels, and IPCC 2006 guidelines for national GHG inventories require the following:

- The amount of GHGs taken up in biomass and the equivalent amount of GHG emissions from the biomass at the point of complete oxidation result in zero net GHG emissions when biomass carbon is not converted into methane, non-methane volatile organic compounds, or other precursor gases.
- GHG emissions from fossil fuel-derived wastes (also called alternative fossil fuels), in contrast, is not a priori climate neutral. Direct GHG emissions from the combustion of alternative fossil fuels shall, therefore, be calculated and included in the total of direct emissions.
- GHG emissions from mixed fuels with biomass and fossil fractions (e.g. pre-treated industrial and/or domestic wastes). a split between the fossil and non-fossil fractions of the fuel, and the emission factors applied to the appropriate fractions.
- CO_{2e} emission factors shall be specified at the plant level where practical. In the absence of any plant or company-specific data, manufacturers shall use the default emission factors provided in the CFP quantification tool in accordance with the IPCC and Cement Sustainability Initiative (CSI).

iii) Combustion of Non-Kiln Fuels

Non-kiln fuels include all fuels which are not covered in the definition of kiln fuels used for cement production. GHG emitted from non-kiln fuels is reported separately, by the following application types, to provide flexibility in the aggregation of emissions:

- Quarrying / mining raw materials
- On-site transportation
- Equipment
- Room heating / cooling
- On-site power generation

Carbon in non-kiln fuels is assumed to be fully oxidised, i.e. carbon storage in soot or ash is not accounted for. The resulting overestimation of emissions will usually be small (approximately 1%) and can be neglected in the CFP assessment. Analogous to the case of kiln fuels, the non-kiln fuels are categorised into conventional, alternative, and biomass fuels for carbon footprint quantification and reporting.

To calculate GHG emissions from non-kiln fuels, fuel consumption, lower heating values and the matching GHG emission factors are required. If available, measured plant-specific lower heating values shall be used. If the same type of fuel is used as non-kiln fuel and kiln fuel, then the CO₂e emission factors used for reporting shall correspond. Otherwise, measured plant-specific emission factors should be used, if available. Alternatively, default values provided in the CFP quantification tool can be applied. When electricity is internally (e.g. On-site generated electricity) produced and consumed for a product under study, life cycle data for that electricity shall be used for that product.

Emissions from Wastewater

Some cement plants inject wastewater in their kilns, for example as a flame coolant to control nitrogen oxides (NO_x). The carbon contained in the wastewater is emitted as CO₂. However, Applicants are not required to quantify their CO₂ emissions related to wastewater consumption, because these emissions are insignificant (usually less than 1% of the plant's overall CO₂ emissions), and difficult to quantify. However, Applicants should be prepared to demonstrate that their wastewater discharge has no significant impact on their overall CO₂ emissions.

WBCSD (2011)

3.3.2.2 Indirect Emissions

Key indirect GHG emissions arising from the production of cement include: i) external production of electricity consumed by cement manufacturers; ii) production of bought raw materials, energy commodities and clinker; iii) off-site transportation of raw materials to manufacturing plant; and iv) land use change.

i) External Electricity Production

When a supplier of grid electricity can deliver a specific electricity product with specific life cycle data and guarantee that the electricity sale and the associated GHG emissions are not double counted, life cycle data for that electricity product shall be used. When the supplier of electricity does not provide specific GHG data for the specific electricity product, the GHG emissions associated with the national grid where the life cycle stage occurs shall be used. Where a country does not have a national grid but has several unconnected grids or several countries share a common grid, GHG emissions associated with the relevant grid from which the electricity is obtained shall be used. If specific life cycle data on a process within the electricity supply system are difficult to access, data from recognised databases may be used.

The GHG emissions shall include: the emissions arising from the generation of electricity, e.g. combustion of fuels and generation of electricity lost in transmission and distribution in the grid; upstream GHG emissions (e.g. the mining and transport of fuel to the electricity generator or the growing and processing of biomass for use as a fuel); downstream GHG emissions (e.g. the treatment of waste arising from the operation of nuclear electricity generators or treatment of ashes from coal fired electricity plants); as well as GHG emissions related to construction, maintenance and decommission of the electricity supply system.

ii) Production of Bought Raw Materials, Energy Commodities and Clinker

GHG emissions and removals associated with the use of raw materials such as limestone, gypsum, clay, etc., in the production and packaging of the finished cement product shall be calculated by multiplying the consumption of those raw materials by the embodied carbon emission factors adopted from the Inventory of Carbon and Energy (ICE) provided in the CFP quantification tool. Primary emission factors should be used if data is available.

GHG emissions from the mining and production of energy commodities such as coal, natural gas, oil, petcoke, etc. used in the cement manufacturing process should also be accounted for under the indirect emissions. Applicants should apply the emission factor provided by region specific databases or well recognised sources (e.g. Ecoinvent, China Energy Statistical Yearbook, Japan CFP database, etc.).

The emissions from the production of clinker shall be assessed based on the net clinker purchases (i.e. bought clinker minus sold clinker) of the Applicant, and the emission factor of the clinker. For clinker transfer within a company, the actual emission factor of the sending plant should be used. If the clinker is bought externally, a default value from the WBCSD GNR website⁵ (WBCSD, 2016) shall be used. As a secondary data, the default emission factor of 862 kg CO₂/t value adopted from Cement Sustainability Initiative (CSI) can be used to calculate the impact of indirect emissions associated with clinker purchases.

iii) Off-site Transportation of Raw Materials to Manufacturing Plant

Applicants are required to specify the mode of transportation (e.g. road, rail, water or aircraft), type of activity data, vehicle type, distance travelled, fuel used, etc. to measure the GHG emissions associated with off-site transportation of raw materials to the manufacturing plant (see Figure 2). When transportation is outside Hong Kong or the fuel consumption of non-road transport is not known, the fuel / distance-based approach is applicable to the case. The transport emissions associated with the cement product can be measured by adopting the WRI and WBCSD's protocol, namely "GHG Emissions from Transport or Mobile Sources"⁶ (version 2.7, 2024) or equivalent resources if deemed appropriate. The fuel-based approach only applies to the case when the transportation happens within Hong Kong and the fuel consumption data are known. The fuel-based emission factors can be obtained from the EPD and EMSD guideline, namely "Guidelines to Account for and Report on Greenhouse Gas Emissions and Removals for Buildings (Commercial, Residential or Institutional Purposes) in Hong Kong"⁷ (2010 Edition). Fuel consumption data can also be estimated based on the energy consumption indicators as provided by EMSD Energy Consumption Indicator⁸.

⁵ The tool is accessible at: <https://www.wbcSD.org/resources/cement-industry-energy-and-co2-performance-getting-the-numbers-right-gnr/>

⁶ The tool is accessible at: <https://ghgprotocol.org/calculation-tools-and-guidance>

⁷ The guidelines are accessible at: www.epd.gov.hk/epd/sites/default/files/epd/english/climate_change/files/Guidelines_English_2010.pdf

⁸ The indicators are accessible at: <https://ecib.emsd.gov.hk/index.php/en/online-benchmarking-tools/transport-sector>

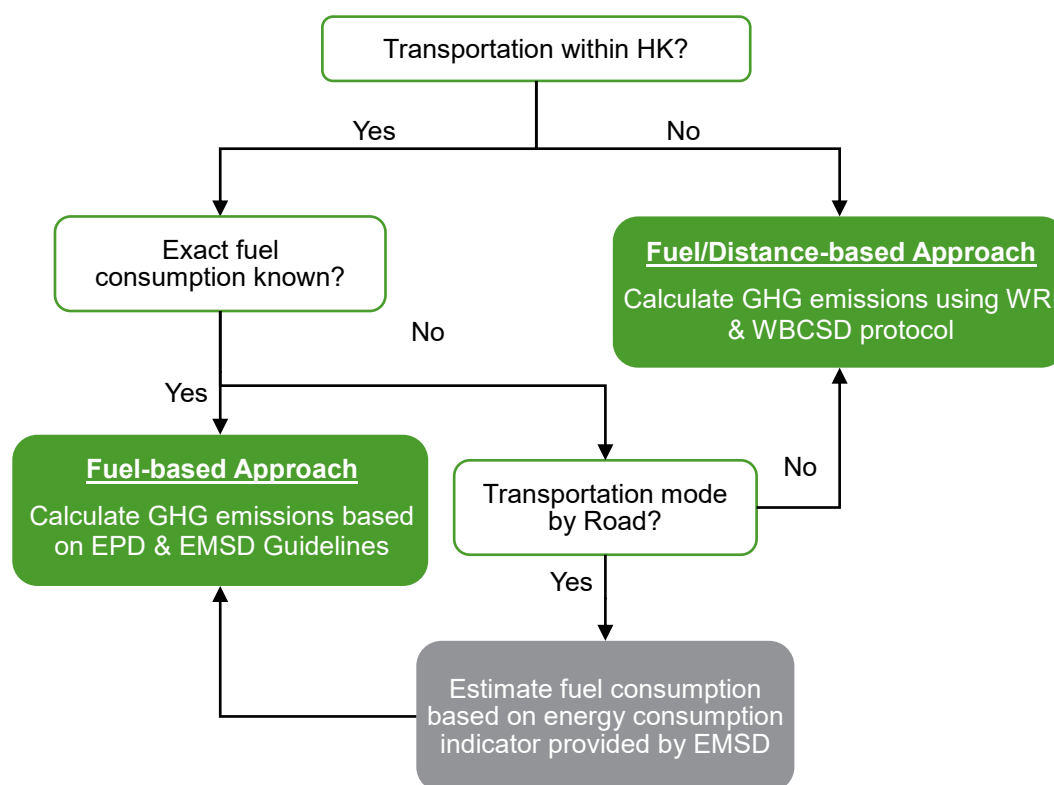


Figure 2 Method Selection for Off-site Transportation Emissions Calculation

iv) Land Use Change

The GHG emissions and removals occurring as a result of direct land use change shall be assessed in accordance with internationally recognised methods such as the IPCC Guidelines for National Greenhouse Gas Inventories and included in the CFP. If plant-specific data are applied, they shall be transparently documented in the CFP study report. If a national approach is used, the data shall be based on a verified study, a peer reviewed study or similar scientific evidence and shall be documented in the CFP study report. Indirect land use change can be ignored in CFP studies under the CIC Green Product Certification.

Table 1 summarises the parameters involved, and the data sources for the calculation of the carbon footprint of cement products.

Table 1: Parameters and Data Sources for Calculating the Carbon Footprint of Cement

	Emission components	Parameters	Units	Sources of parameters
Direct Emissions	Raw Materials Calcination and Combustion			
	Calcination of raw materials for clinker production	Clinker produced	t	Measured at plant level Default = 525; or corrected according to the measured CaO and MgO contents of clinker
		Emission factor clinker	kg CO ₂ /t clinker	
	Calcination of dust	Dust leaving kiln system	t	Measured at plant level Calculated as detailed in Section 3.3.2
		Emission factor clinker	tCO ₂ /t clinker	
	Combustion of total organic carbon	Clinker produced	t	Measured at plant level Default = 1.55 (can be adjusted) Default = 0.2% Default = 3.667 (or 44/12)
		Raw meal: clinker ratio	fraction	
		TOC content of raw meal Conversion factor for carbon to carbon dioxide	t / t clinker tCO ₂ /t	
	Kiln and Non-Kiln Fuel Combustion			
	Conventional kiln fuels	Fuel consumption	t	Measured at plant level Measured at plant level IPCC/CSI defaults, or measured
Lower heating value		GJ/t fuel		
Emission factor		tCO ₂ e/GJ fuel		
Alternative fossil fuels	Fuel consumption	t	Measured at plant level Measured at plant level CSI defaults, or measured	
	Lower heating value	GJ/t fuel		
	Emission factor	tCO ₂ e/GJ fuel		
Biomass fossil fuels	Fuel consumption	t	Measured at plant level Measured at plant level Default = 0 kg CO ₂ e	
	Lower heating value	GJ/t fuel		
	Emission factor	tCO ₂ e/GJ fuel		
Indirect Emissions	External electricity production	Power bought from external grid	GWh	Measured at plant level Applicant-specific value or country grid factor
		Emission factor	tCO ₂ e/GWh	
	Production of bought raw materials, energy commodities and clinker	Net raw materials, energy commodities and clinker purchased	t	Measured at plant level Default factor / Input
		Emission factor	tCO ₂ e/t	
	Off-site transportation of Raw Materials to Manufacturing Plant	Mode of transportation		Measured using WRI & WBCSD protocol / EPD&EMSD Guidelines
		Type of activity data		
Vehicle type				
Distance travelled				
Land use change	Fuel consumed		Measured in accordance with IPCC Guidelines	
	Emission factor			

3.3.3 *Guidelines for Inclusion of Similar Products*

If the discrepancies in environmental performance indicators among the declared products do not exceed 10%, similar products manufactured at one or multiple locations owned by the same company that fall under the same Product Category Rule may be incorporated under a single group product certification, contingent upon the core manufacturing processes being fundamentally the same.

Additionally, when preparing the application, the Applicant must ensure the following:

- The products must share identical chemical and mechanical properties, such as chemical composition and compressive strength.
- All products included in the same group product certification must fall within the same rating category of Carbon Label.

Once the Applicant chooses to apply through the group certification, the data reporting for the grouped products shall follow either one of the below approaches.

- **Weighted Average Calculation:** The average must be weighted according to the production volumes of the included products, if applicable. This means that products with higher production volumes will have a greater influence on the overall average, providing a more accurate representation of environmental performance.
- **Worst-Case Reporting:** If a single value is selected for each impact category across all products, the reported value should reflect the worst performance within the range of variation.

4. REQUIREMENTS

All submissions and documentations shall be endorsed by the Chief Executive Officer or other authorised persons of the Applicant to demonstrate conformance to the assessment criteria. All certification, laboratory reports, and documentation must be valid during the assessment process and labelling period. The date of issue of all laboratory reports and documentation shall be within 5 years from the first application submission date.

If the certification expires during the labelling period or upon renewal, the applicant is required to provide an updated and valid certification. Failure to resubmit the required certification will result in the revocation of CIC Green Product Certificate without compensation.

The chemical tests should be conducted by either a third party or the manufacturer, providing that they have obtained ISO 17025 certification or relevant national accreditations, such as HOKLAS or CNAS.

4.1 CARBON

4.1.1 CFP Quantification - Core Criteria

The applicant is required to achieve 50 Basic Points under this section. Additionally, the applicant can achieve a maximum of 40 Bonus Points under this section.

Requirements

The Applicant shall provide a life cycle assessment report for quantification and reporting of the carbon footprint of products (CFP), following the guidance addressed in the General Requirements and detailed system boundary and GHG emissions related to the raw material used listed in Section 3. The CFP study report should be prepared in accordance with ISO 14067:2018 or GB/T 24067-2024.

OR

The Applicant shall provide the product's CFP value from a product-level EPD certified in accordance with ISO 14025:2006, ISO 14067:2018, or BS EN 15804:2012, ISO 21930:2017, GB/T 24025-2009 or GB/T 24067-2024. The EPD shall demonstrate the GHG emissions covering the system boundary specified in Section 3.

The benchmark for Cement products is listed in Table 2 below.

*Table 2: Benchmark for Cement
(The values shall be rounded to three decimal places)*

Points	CFP (tCO _{2e} / t of product)
50 Basic + 40 Bonus	≤0.658
50 Basic + 30 Bonus	0.659-0.790
50 Basic + 20 Bonus	0.791-0.966

50 Basic + 10 Bonus	0.967-1.097
50 Basic	≥1.098

Verification

To obtain the points under this criterion, the following documents shall be provided for verification:

- CFP quantification report in accordance with ISO 14067:2018, GB/T 24067-2024, OR
- Product-level Environmental Product Declaration (EPD) in accordance with ISO 14025:2006, ISO 14067:2018, BS EN 15804:2012, ISO 21930:2017, GB/T 24025-2009 or GB/T 24067-2024

4.2 RESOURCE

4.2.1 Waste Management – Non-core Criteria

The Applicant can achieve 5 Bonus Points under this section.

Requirements

The Applicant shall provide a waste management plan that outlines effective policies and procedures to minimise waste and recycle waste materials from manufacturing, and a waste audit report that includes measurement of solid waste generated and managed to divert from landfills. This report should cover the last 12 months⁹ and include the following:

- (i) Quantities and types of waste recovered for on-site usage; and
- (ii) Quantities and types of waste diverted from landfills (e.g. to the recycling facility, sorting facility, public fill, etc.); and
- (iii) Quantities and types of waste disposed of to landfills; information and disposal locations for all wastes; and
- (iv) Initiatives taken to reduce waste generation and improve recovery/recycling of waste.

Verification

To obtain the points under this criterion, the following documents shall be provided for verification:

- A waste management plan and a waste audit report with data support, including but not limited to trip tickets to downstream recyclers, shall be provided for verification.

⁹ If the manufacturer has not been in operation for 12 months, the period can be appropriately shortened but should not be less than 6 months.

4.3 ENVIRONMENT

4.3.1 Regional Materials – Non-core Criteria

The Applicant can achieve 5 Bonus Points under this section.

Requirements

Products that achieve a 95% localisation degree of raw materials will be granted 5 bonus points. The localisation degree of raw materials is calculated based on the percentage of materials transported within certain distances with appropriate transportation methods.

The calculation focuses on the primary raw materials, according to formula below.

$$T = \frac{M_{gt}}{M_t} \times 100\%$$

where:

T = The localisation rate of raw materials

M_{gt} = The total quantity of primary raw materials used during the statistical period, transported to the manufacturer, within 800km radius by road transportation; within a 1,600km radius by rail transportation; or within a 4,000km radius by sea transportation, excluding water, measured in tons (t). The distance is measured by the direct distance, not by actual travel distance.

M_t = The total amount of raw materials used during the statistical period, excluding water, measured in tons (t).

A statistical period of 12 months should be used. If the manufacturer has not been in operation for 12 months, the period can be appropriately shortened but should not be less than 6 months.

Verification

To obtain the points under this criterion, the following documents shall be provided for verification:

- A self-prepared calculation report with relevant supporting documentation, including but not limit to, purchase order forms showing the quantity of raw materials used, a map showing the origin for each raw material, the location of the plant, and the transportation methods.

4.4 PERFORMANCE

4.4.1 Advancement – Non-core Criteria

The Applicant can achieve 5 Bonus Points under this section.

Requirements

Products that achieve a valid “Product Conformity Certification Scheme for Cement Products” certificate will be granted 5 bonus points. The assessment body¹⁰ shall be accredited by the Hong Kong Accreditation Service (HKAS) or its Mutual Recognition Agreement (MRA) partners in accordance with this scheme and ISO/IEC 17065:2012 standards.

Verification

To obtain the points under this criterion, the following documents shall be provided for verification:

- Valid certificate of Product Conformity Certification Scheme for Cement Products.

4.5 INNOSMART

4.5.1 Innovations & Additions – Non-core Criteria

The Applicant can achieve 5 Bonus Points under this section.

Requirements

Manufacturers who exceed the basic requirements can earn 5 bonus points by showcasing innovative, sustainable production practices.

Examples of incorporating various innovative and smart technologies to improve efficiency, reduce energy consumption, and optimise performance are given in Table 3.

Table 3: Example of innovative and smart technologies

Examples	Descriptions
Decarbonisation Strategies	<ul style="list-style-type: none"> • CO₂ Capture Technologies: Implement carbon capture and storage (CCS) technologies that capture CO₂ emissions from cement production. This captured CO₂ can be reused in other processes or stored underground. • Carbon Mineralisation: Some manufacturers are exploring using captured CO₂ to create stable carbonates, which can be used as a raw material in cement.
Environmental Impact Reduction	<ul style="list-style-type: none"> • Energy Efficiency: Employ energy-efficient technologies in the kiln, such as preheaters, to reduce fuel consumption. • Alternative Fuels: Use renewable or waste-derived fuels (e.g., biomass, industrial waste) in the kiln to replace fossil fuels, lowering carbon emissions.

¹⁰ The certification body list accredited by HKAS is accessible from https://www.hkctc.gov.hk/en/tcsector/ba/construction_product_cert_c.html

Verification

To obtain the points under this criterion, the following documents shall be provided for verification:

- Submit a writing report (maximum of 1000 words). The report should outline the solution, objectives, and evaluation to meet the criteria set by smart technologies; and
- The attachment should contain evidence of implementation and the technical specifications.

5. SCORING

The points for meeting each criterion stated in this Standard are summarized below.

Table 4: Points to be awarded under the assessment criteria of this Standard

Label	Evaluation criteria	Points		Related HK Beam Plus Credits
		Basic	+Bonus	
Carbon	CFP Quantification [CORE]	50	+10/+20/ +30/+40	MW 10
Resource	Waste Management	-	+5	
Environment	Regional Materials	-	+5	MW 8
Performance	Advancement	-	+5	
InnoSmart	Innovations & Additions	-	+5	IA
Total: (Maximum possible:100)		50	+50	

Applicants must demonstrate that they have achieved the basic points under the CORE criteria. They may also apply for other sustainability labels beyond the Carbon Label. However, only a maximum of 10 bonus points from any combination of TWO labels will be included in the final score for their rating. These bonus points can be earned from any assessment criteria under the Resource, Environment, Performance, and InnoSmart Labels.

Related BEAM Plus Credits refer to these relevant credits under BEAM Plus New Buildings Version 2.0, as listed below.

- MW 8: Regional Materials
- MW 10: Life Cycle Assessment
- Innovations and Additions

6. REFERENCES

BS EN 197-1 (2011) Composition, Specifications and Conformity Criteria for Common Cements.

Cement Sustainability Initiative. Available from <http://www.ghgprotocol.org/files/ghgp/public/ghg-protocol-revised.pdf>

EPD & EMSD (2010). Guidelines to Account for and Report on Greenhouse Gas Emissions and Removals for Buildings (Commercial, Residential or Institutional Purposes) in Hong Kong. Available from https://cnsd.gov.hk/wp-content/uploads/2023/05/Guidelines_English_2010.pdf

EPD (2024) Product Category Rules for Cement and building lime, The International EPD® System.

GB/T 24067-2024 Greenhouse gases : Product carbon footprint Quantification requirements and guidelines.

IEA (2018) Technology Roadmap-Low-Carbon Transition in the Cement Industry. International Energy Agency, France.

IPCC (2006) *Guidelines for National Greenhouse Gas Inventories*. National Greenhouse Gas Inventories Programme, Intergovernmental Panel on Climate Change.

ISO 14025 (2006) Environmental Labels and Declarations – Type III Environmental Declarations – Principles and Procedures.

ISO 14040 (2020) Environmental Management – Life Cycle Assessment – Principles and Framework.

ISO 14044 (2020) Environmental Management – Life Cycle Assessment – Requirements and Guidelines.

ISO 14064-1 (2018) Greenhouse Gases – Part 1: Specification with Guidance at the Organization Level for Quantification and Reporting of Greenhouse Gas Emissions and Removals.

ISO 14067 (2018) Greenhouse Gases – Carbon Footprint of Products – Requirements and Guidelines for Quantification and Communication.

Lindstad, T., Olsen, S.E., Tranell, G., Færden, T. and Lubetsky, J. (2007) Greenhouse Gas Emissions from Ferroalloy Production, *International Ferro-Alloys Congress (INFACON XI)* New Delhi, India, 18-21 February 2007.

United Nations (2020) The Doha Amendment to the Kyoto Protocol. New York: United Nations.

WBCSD (2011) CO₂ and Energy Accounting and Reporting Standard for the Cement Industry, The Cement CO₂ Protocol Version 3, World Business Council for Sustainable Development / Cement Sustainability Initiative.

WBCSD (2013a) Global Cement Database on CO₂ and Energy Information, “Getting the Numbers Right (GNR)”. Accessed on 26 Oct. 2013 from <http://www.wbcscement.org/index.php/key-issues/climate-protection/gnr-database>

WBCSD (2013b) Greenhouse Gas Protocol, A Corporate Accounting and Reporting Standard, Revised Edition. World Business Council for Sustainable Development /

WBCSD (2016). “Cement Industry Energy and CO₂ Performance: Getting the Numbers Right (GNR)”. Available from <https://www.wbcsd.org/resources/cement-industry-energy-and-co2-performance-getting-the-numbers-right-gnr/>

WRI (2024) “GHG Emissions from Transport or Mobile Sources”. Available from <https://ghgprotocol.org/calculation-tools-and-guidance>